

Content available at: <https://www.ipinnovative.com/open-access-journals>

Indian Journal of Pharmacy and Pharmacology

Journal homepage: <https://www.ijpp.org.in/>

Original Research Article

Synthesis of zinc ferrite nanoparticles and evaluation of their antifungal properties at different temperatures

Jyothish Babu¹, John Jacob^{1,*}, Nisha S Thulasi¹, Keerthi Mohandas¹

¹Dept. of Physics, Mar Ivanios College, Thiruvananthapuram, Kerala, India



ARTICLE INFO

Article history:

Received 24-11-2022

Accepted 15-12-2022

Available online 09-03-2023

Keywords:

Zinc ferrite

XRD

Spectroscopy

Nanoparticles and FTIR

ABSTRACT

Zinc ferrite nanoparticles have been synthesized by the co-precipitation method where Polyethylene Glycol act as the capping agent. The sample structure and morphology of the product were analysed by powder XRD, FTIR, U-V visible spectroscopy and scanning electron microscope (FE-SEM). The prepared NPs were annealed at varying temperatures such as 500°C, 600°C and 700°C. The XRD data confirms the presence of nanosized ZnFe₂O₄ particles and the X-ray density of the sample and their particle size increases linearly along with the increase in annealing temperature, but the lattice parameter changes inversely. The FTIR data also provide information about nanosized zinc ferrite particles. The surface characteristics of ZnFe₂O₄ were observed by FESEM. The anti-fungal properties of zinc ferrite nanoparticles were also evaluated.

This is an Open Access (OA) journal, and articles are distributed under the terms of the [Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License](https://creativecommons.org/licenses/by-nc-sa/4.0/), which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

For reprints contact: reprint@ipinnovative.com

1. Introduction

The most positive feature of nanotechnology is the anomalous properties including soft magnetic nature and magnetic nanoparticles at various compositions.^{1,2} They contribute typical applications in different technological and fundamental research areas such as bio-medical, and bio-processing and are used as a good catalyst among many other NPs.³⁻⁵ Among the spinel ferrite compounds zinc ferrite exhibits superparamagnetic behaviour and prospective applications in many fields including photocatalysis, Magnetic Resonance Imaging (MRI), Li-Iron batteries and gas sensors. Various synthesis methods are proposed to prepare ZnFe₂O₄ nanoparticles such as the coprecipitation method, thermal decomposition, solvothermal, hydrothermal and ball milling. In this work superparamagnetic ZnFe₂O₄ NPs were synthesized by adopting the method of Co-

precipitation method. Polyethylene glycol act as a capping element for the synthesis.⁶⁻⁸ The most auspicious feature of nanotechnology is the magnetic nano parties of different compositions. Since they have applications in the biomedical field and have catalytic properties, it is significant to get further detailing about Zn ferrite nanoparticles and to enhance the application level or develop new one's careful studies based on their functional sample size and also along with that their antifungal behaviour is essential. Among the spiral ferrite compounds, zinc ferrite exhibits superparamagnetic behaviour and it has prospective applications in many fields. Such as photocatalysis, magnetic reasonable imaging, Lithium — ion batteries and gas sensors.^{9,10}

In the present paper, to characteristics structure and morphology of nanoparticles by using XRD, FTIR, U. V visible spectroscopy. To assess the properties of synthesized nanoparticles by antifungal using the Agar-well diffusion method.

* Corresponding author.

E-mail address: john.jacob.mic@gmail.com (J. Jacob).

2. Synthesis

2.1. Zinc ferrite nanoparticles is prepared as follows

Here we use one mol of ferric nitrate, one mol of zinc nitrate, 0.1 mol of polyethylene glycol (PEG), one mol of sodium hydroxide (NaOH), one mol of ammonium carbonate, Ferric nitrate and zinc nitrate are taken in a clean burette and the aluminium nitrate is taken in a clean pipette, while the rest of others are mixed well in a beaker and is subjected to magnetic stirring where all these get stirred well. Allow the solution from the burette to fall on the solution drop by drop and the colour of the solution begins to change. Once the stirring is over, the solution is removed from to test tubes and centrifugation is performed at a rate of 4000rpm for 15 minutes then settled precipitate is washed and separated from the test tubes. After that, it is heated to remove its water content and then it is crushed into powder using mortar. The powder is then heated using a muffle furnace at altered temperatures (500, 600 & 700°C) continuous for up to 4 hours to get the required aluminium doped zinc ferrite nanoparticle.

3. Results

3.1. XRD analysis

The crystallographic structure of the obtained ZnFe_2O_4 nanoparticles was identified by using XRD data. Average particle size, the lattice parameter and X-ray density can be measured.^{11–14}

All the samples show diffraction peaks at (311) compared with the JCPDS card No: 82-1049, which confirms the synthesized product single-phase cubic in synthesized nanoparticles. The crystallite size can be measured using the shearer's equation. From Table 1 we observe that when temperature increases the crystallite size and particle size also increase while the lattice parameter decreases. The X-ray density increases with the increasing temperatures from 500°C to 700°C.

3.2. FE-SEM analysis

The FESEM images exhibit agglomerated branches of spherical shaped nanoparticles, because of their high surface energy. The FESEM images show that thus agglomeration of zinc ferrite nanoparticles because of the effect of the capping agent on modifying crystal size.^{15–17}

3.3. FTIR analysis

All samples exhibited peaks near 530 cm^{-1} corresponding to the Fe-O stretching frequency near 425 cm^{-1} peaks indicated zinc ferrites nanoparticle. The present study suggests a linear variation between crystallite size and temperatures. This observation from the FTIR study strongly supports the result observed by XRD values. All samples have absorption

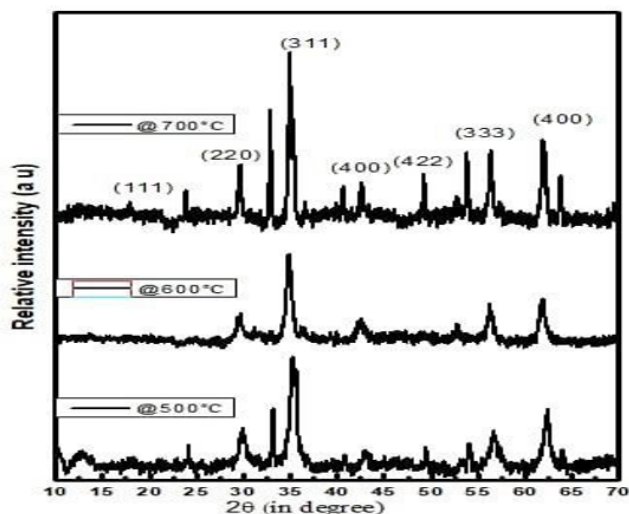


Fig. 1: The XRD pattern of ZnFe_2O_4 nanoparticles synthesized at 500°C, 600°C and 700°C. The graph shows XRD analysis at different temperatures. The observed peak position and intensities showed that all the samples had the finite structure.

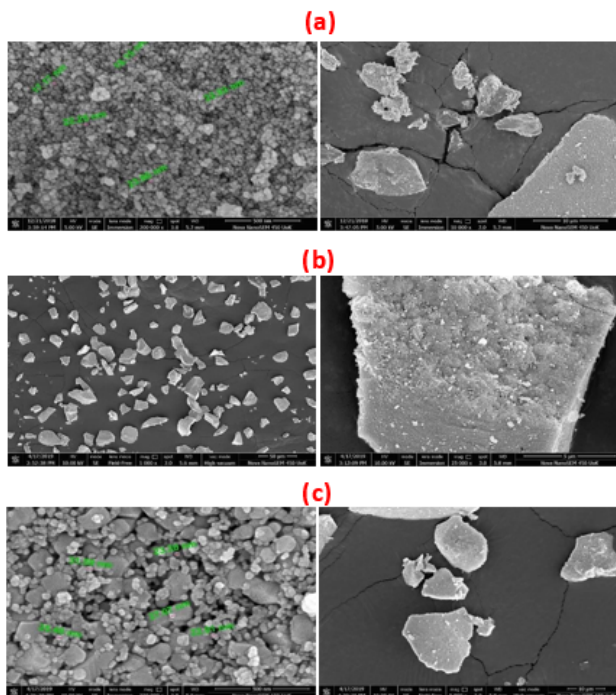


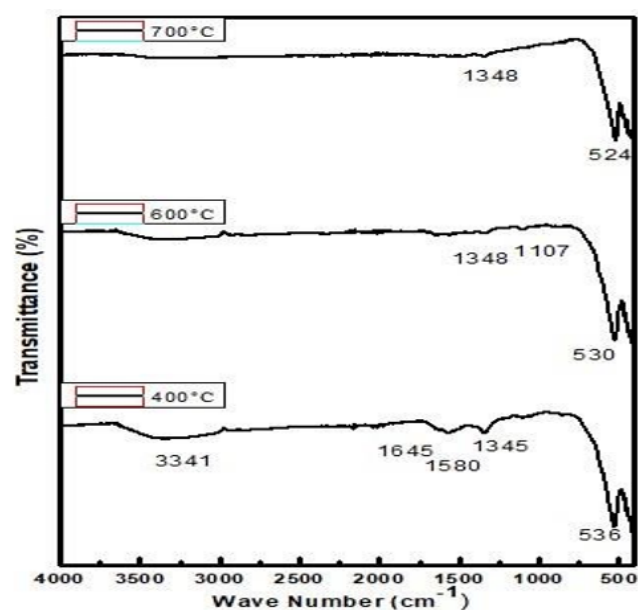
Fig. 2: FE-SEM Images (a) at 500°C (b) 600°C (c) 700°C

Table 1: The values of crystalline size (nm), particle size (nm) in FE-SEM, lattice constant(a), X-ray density, cell volume and specific surface area (S)

Temperature	Crystallite size in (nm) XRD	Particle size in (nm) FE-SEM	Lattice constant (a) value in (Å)	X-ray density dx(g/cm ³)	Unit cell Volume (a) ³	Specific surface area (S) (m ² /g)
500 ⁰ C	5.99	4.48	8.44135	5.3241	601.499	18.846
600 ⁰ C	6.615	5.06	8.41585	8.374	596.062	16.92
700 ⁰ C	10.39	9.59	8.38155	5.438	588.805	10.64

Table 2: The values of bond length A-O (Å), bond length B-O (Å), ionic radius rA and ionic radius rB

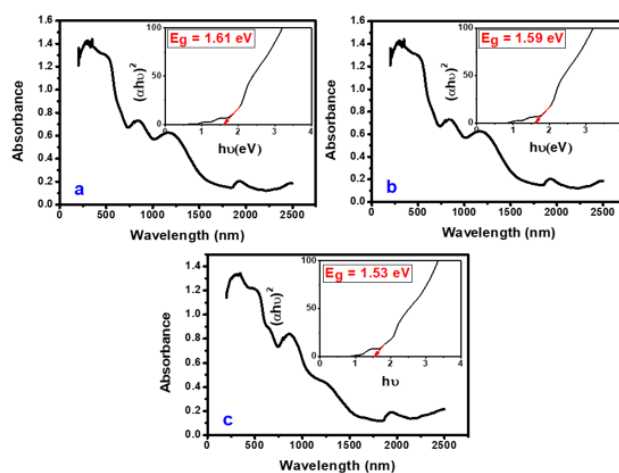
Temperature	Bond Length in A-O sites (Å)	Bond Length in B-O sites (Å)	Ionic radius rA (Å)	Ionic radius rB (Å)
500 ⁰ C	3.66	5.2	4.98	5.714
600 ⁰ C	3.64	5.26	4.96	5.7
700 ⁰ C	3.63	5.24	4.95	5.66

**Fig. 3:** FTIR spectra of zinc ferrite nanoparticles annealed at 400⁰C, 600⁰C, and 700⁰C are shown.

bands in the region of 500-550 cm⁻¹ and 400-450 cm⁻¹. The high-frequency band is due to the stretching vibration of the unit cell in the tetrahedral A sites and the lower is due to the metal-oxygen in the octahedral B site i.e., high- the frequency band is due to the Zn-O stretching and the lower frequency corresponds to Fe-O stretching which confirms the formation of ZnFe₂O₄ nanoparticles. From the spectrum, some other absorption bands are also observed in the range 3750-3000 cm⁻¹, 1750-1500 cm⁻¹ and 1500-1250 cm⁻¹ representing stretching frequencies of N-H bond and C=O and also O-H stretching vibrations respectively. As the temperature increases the bonds other than Zn-O, Fe-O and O-H bonds disappear. The appearance of the O-H bond indicates the presence of water in the sample.¹²⁻¹⁵

3.4. U-V analysis

The change in characteristic properties of the synthesized sample towards the effect of light was investigated by UV-Visible spectral data. Figure 4 shows the spectra in the sample range of wavelength 200-800 nm. Band gap energy obtained for ZnFe₂O₄ is reducing with an increase in temperature.

**Fig. 4:** Tauc plot of zinc ferrite samples (a) at 500⁰C (b) at 600⁰C and (c) at 700⁰C

3.5. Anti-fungal analysis agar-well diffusion method

The Biological activity and antifungal ability of samples were estimated by conducting Agar well diffusion technique. For that purpose, the analysing samples have purposefully interacted with test organisms that are seeded in a test plate.^{16,17} The results were obtained in the form of a circular zone of inhibition. The results were evaluated according to the diameter of the zone. The test plates were kept overnight for the growth of species. *Aspergillus Niger* was considered as a standard for the analysis.

Wells of nearly 10 mm was used and samples of varying concentration such as 25µg/mL and 1000µg/ mL were added to these wells. The circular zone of inhibition was estimated after incubation at room temperature overnight and compared with that of the standard. From the antifungal activity of the prepared samples, it was found that they are active against the fungal pathogen *Aspergillus Niger* except at 700°C. We can conclude as the temperature increases the zone of inhibition reduces and at 700°C it will inactive.

Table 3: The antifungal activity of zinc ferrite nanoparticles at different concentration 250µg/ml, 500µg/ml, 1000µg/ml at 500°C

Sample	Concentration (µg/ml)	Zone of exhibition (mm)
500°C	250	Nil
	500	12
	1000	14
Clotrimazole	100	21

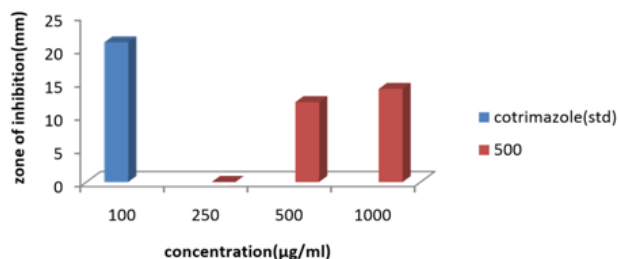


Fig. 5: Anti-fungal analysis of zinc ferrite NPs at 500°C

Table 4: The antifungal activity of zinc ferrite nanoparticles at different concentration 250µg/ml, 500µg/ml, 1000µg/ml at 600°C

Sample	Concentration (µg/ml)	Zone of exhibition (mm)
600°C	250	Nil
	500	12
	1000	14
Clotrimazole	100	26

Table 5: The antifungal activity of zinc ferrite nanoparticles at different concentration 250µg/ml, 500µg/ml, 1000µg/ml at 700°C

Sample	Concentration (µg/ml)	Zone of exhibition (mm)
700°C	250	Nil
	500	Nil
	1000	Nil
Clotrimazole	100	21

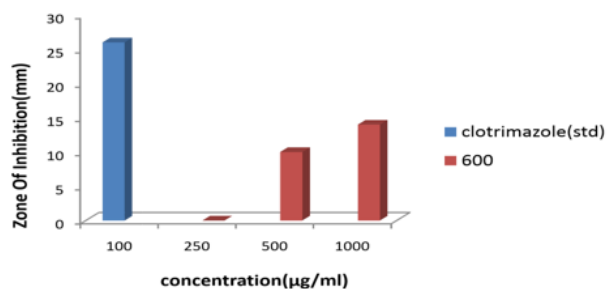


Fig. 6: Antifungal activity of zinc ferrite NPs at 600°C

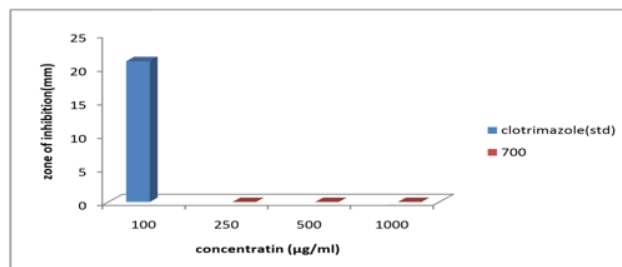


Fig. 7: Anti-fungal analysis of zinc ferrite NPs at 700



Fig. 8: Anti-fungal analysis of zinc ferrite NPs at 500°C, 600°C and 700°C.

4. Conclusion

Zinc ferrite nanoparticles were successfully prepared by the coprecipitation method using PEG as a capping agent. The XRD confirms the crystal structure and phase purity of the sample. The FESEM of ZnFe₂O₄ nanoparticles shows the spherical agglomerated particles' antifungal activity showed the application of zinc ferrite NPs in inflammation and cancer therapy. FTIR study confirmed the presence of zinc ferrite NPs at all annealing temperatures. The optical study uses UV visible spectroscopy and can notice with the increase in temperature the bandgap energy decreases. From the antifungal activity of the prepared samples, it was found that they are active against the fungal pathogen *Aspergillus Niger* except at 700°C.

5. Source of Funding

None.

6. Conflicts of Interest

The authors have no conflicts of interest.

7. Acknowledgment

We are very much acknowledged to CLIF, University of Kerala, NCESS, Thiruvananthapuram.

References

- Mudshinge SR, Deore AB, Patil S, Bhalgat CM. Nano particles: emerging carriers for drug delivery. *Saudi Pharm J*. 2011;19(3):12–70.
- Krishnan K. Biomedical nano magnetics: a spin through possibilities in imaging, diagnostics, and therapy. *IEEE Trans Magn*. 2010;46(7):2523–58.
- Tartaj P, Morales M, Verdaguier SV, alez TG, Serna C. The preparation of magnetic nanoparticles for applications in biomedicine. *J Phys D*. 2003;36(13):182. doi:10.1088/0022-3727/36/13/202.
- Faraji M, Yamini Y, Rezaee M. Magnetic nanoparticles: synthesis, stabilization, functionalization, characterization, and applications. *J Iran Chem Soc*. 2010;7:1–37.
- Indira TK, Lakshmi MK. Magnetic nanoparticles-a review. *Int J Pharm*;
- Chu A, Foster M, Hancock D, Bell-Anderson K, Petocz P, Samman S. TNF- α gene expression is increased following zinc supplementation in type 2 diabetes mellitus. *Genes Nutr*. 2015;40(1):440. doi:10.1007/s12263-014-0440-4.
- Jyothsh B, Jacob J. Al-doped zinc ferrite nanoparticles: Preparation and evaluation of thermal, structural, morphological and anti-cancer properties. *J Alloys Compounds*. 2021;863:158352. doi:10.1016/j.jallcom.2020.158352.
- Tatarchuk T, Paliychuk ND, Bououdina M, Al-Najar M. Preparation of cobalt–zinc ferrite (Co_{0.8}Zn_{0.2}Fe₂O₄) nanopowder via combustion method and investigation of its magnetic properties. *Mater Res Bull*. 2010;45(12):1792–5.
- Librelotto N, Lais E, Scheeren LB, Macedo MP, Vinardell CM. pH-Sensitive chitosan-tripolyphosphate nanoparticles increase doxorubicin-induced growth inhibition of cervical HeLa tumor cells by apoptosis and cell cycle modulation. *Colloids Surf B Biointerfaces*. 2020;190:110897. doi:10.1016/j.colsurfb.2020.110897.
- Sigh S, Singhal S. Transition metal doped cobalt ferrite nanoparticles: Efficient photocatalyst for photodegradation of textile dye. *Mater Today Proc*. 2019;14(2):453–60.
- Hosseini S, Sarsari I, Kameli P, Salamati H. Effect of Ag doping on Structural, Optical and photocatalytic properties of ZnO nanoparticles. *J Alloys Compounds*. 2015;640(15):408–15.
- Kumar R, Singh RR, Barman P. Cobalt doped zinc ferrite Nanoparticles- XRD analysis an insight. *Int J Sci Eng Res*. 2014;5(5):12–20.
- Rani BJ, Ravi Y, Kumar V, Yuvakkumar R, Ganesh V. Pure and cobalt substituted zinc ferrite ceramics for Super capacity application. *Applied Physics A*. 2018;124(7):124–511.
- Lin Q, Lin J, He Y, Wang R. Jianghui Dong; The structural and magnetic properties of Gadolinium doped CoFe₂O₄ nano ferrites. *J Nanomaterials*. 2015;p. 1–6. doi:10.1155/2015/294239.
- Jyothish B, Jacob J. Effect of temperatures on structural on structural, morphological and bio -properties of zinc ferrite nanoparticles. *IJPSR*. 2020;54:6391–401.
- Shoueir MK, Ahmed SA. Thallium and selenite doped carbonated hydroxyapatite: Microstructural features and anticancer activity assessment against human lung carcinoma. *Ceramics Int*. 2020;46(4):5201–12.
- Jyothish UB, Geethu J. Influence of Ag¹⁺ and Co²⁺ doping on structural, optical and anti-cancer properties of ZnFe₂O₄ nanoparticles synthesized by co-precipitation method. *Mater Sci Eng B*. 2022;276:115544.

Author biography

Jyothish Babu, Assistant Professor

John Jacob, Assistant Professor

Nisha S Thulasi, Student

Keerthi Mohandas, Student

Cite this article: Babu J, Jacob J, Thulasi NS, Mohandas K. Synthesis of zinc ferrite nanoparticles and evaluation of their antifungal properties at different temperatures. *Indian J Pharm Pharmacol* 2023;10(1):28–32.